

English Version

## Aluminium and aluminium alloys - Cold drawn rod/bar and tube - Part 8: Porthole tubes, tolerances on dimensions and form

Aluminium et alliages d'aluminium - Barres et tubes  
étirés - Partie 8 : Tubes filés à pont, tolérances sur  
dimensions et forme

Aluminium und Aluminiumlegierungen - Gezogene  
Stangen und Rohre - Teil 8: Mit Kammerwerkzeug  
Stranggepresste Rohre, Grenzabmaße und  
Formtoleranzen

This European Standard was approved by CEN on 11 April 2016.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN-CENELEC Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION  
COMITÉ EUROPÉEN DE NORMALISATION  
EUROPÄISCHES KOMITEE FÜR NORMUNG

**CEN-CENELEC Management Centre: Avenue Marnix 17, B-1000 Brussels**

<b>Contents</b>	<b>Page</b>
European foreword.....	3
<b>1 Scope</b> .....	<b>4</b>
<b>2 Normative references</b> .....	<b>5</b>
<b>3 Tolerances on dimensions</b> .....	<b>5</b>
3.1 General.....	5
3.2 Diameter - Round tube.....	5
3.3 Width, depth or width across flats - squares, rectangles, hexagons, octagons.....	6
3.4 Wall thickness variation (eccentricity).....	7
3.5 Length.....	8
3.6 Squareness of cut ends.....	9
<b>4 Tolerances on form</b> .....	<b>9</b>
4.1 General.....	9
4.2 Straightness.....	9
4.3 Convexity-Concavity.....	10
4.4 Twist.....	11
4.5 Angularity.....	12
4.6 Corner and fillet radii.....	13
4.7 Depth of dents for round tubes.....	13
<b>Annex A (informative) Wall thickness variation (eccentricity)</b> .....	<b>15</b>
A.1 General.....	15
A.2 Specifying round tube sizes and tolerances.....	15
<b>Bibliography</b> .....	<b>17</b>

## European foreword

This document (EN 754-8:2016) has been prepared by Technical Committee CEN/TC 132 “Aluminium and aluminium alloys”, the secretariat of which is held by AFNOR.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by December 2016, and conflicting national standards shall be withdrawn at the latest by December 2016.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN [and/or CENELEC] shall not be held responsible for identifying any or all such patent rights.

This document supersedes EN 754-8:2008.

The following technical modifications have been introduced during the revision:

— Subclause 3.2 Diameter - Round tube.

EN 754 comprises the following parts under the general title *Aluminium and aluminium alloys — Cold drawn rod/bar and tube*:

- *Part 1: Technical conditions for inspection and delivery;*
- *Part 2: Mechanical properties;*
- *Part 3: Round bars, tolerances on dimensions and form;*
- *Part 4: Square bars, tolerances on dimensions and form;*
- *Part 5: Rectangular bars, tolerances on dimensions and form;*
- *Part 6: Hexagonal bars, tolerances on dimensions and form;*
- *Part 7: Seamless tubes, tolerances on dimensions and form;*
- *Part 8: Porthole tubes, tolerances on dimensions and form.*

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and the United Kingdom.

## 1 Scope

This European Standard specifies the tolerances on dimensions and form for aluminium and aluminium alloy cold drawn porthole tubes with an outside diameter (*OD*) from 3 mm to 350 mm (round tube, see Figure 1) or with a cross section contained within a circumscribing circle (*CD*) from 8 mm to 300 mm (other than round tube, see Figure 2), supplied in straight lengths.

This document only applies to cold drawn tube for general engineering applications made in the following alloys:

- EN AW-1050A, EN AW-1200;
- EN AW-3003, EN AW-3103;
- EN AW-5005, EN AW-5005A, EN AW-5049, EN AW-5251, EN AW-5052;
- EN AW-6012, EN AW-6060, EN AW-6061, EN AW-6262, EN AW-6262A;
- EN AW-6063, EN AW-6063A, EN AW-6065, EN AW-6082;
- EN AW-7020.

The temper designations used in this part are according to EN 515.

This document only applies to tube produced by the porthole/bridge method of extrusion only (and then cold drawn to the final dimensions).

This document does not apply to:

- cold drawn tubes produced by the seamless, die/mandrel method (EN 754-7),
- tubes delivered in coils (EN 13958),
- coiled tubes cut to length (EN 13958).


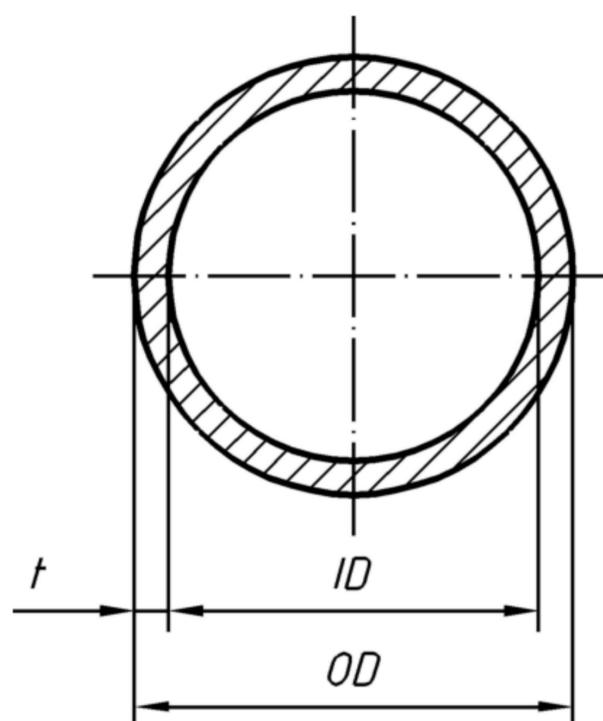


Figure 1 — Round tube

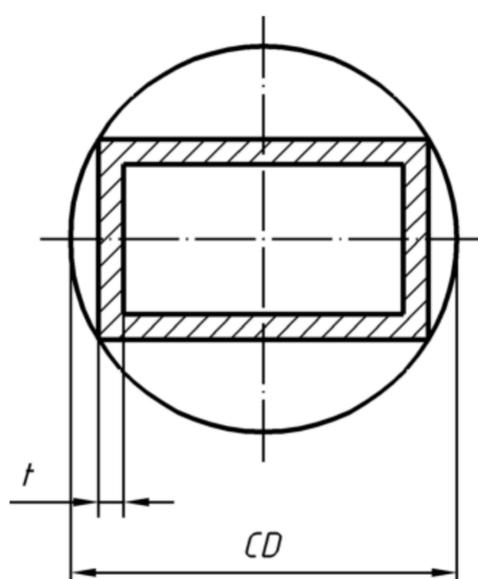

**Figure 2 — Circumscribing circle for other than round tube**

## 2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

EN 754-1:2016, *Aluminium and aluminium alloys — Cold drawn rod/bar and tube — Part 1: Technical conditions for inspection and delivery*

## 3 Tolerances on dimensions

### 3.1 General

When outside diameter  $OD$ , inside diameter  $ID$ , and wall thickness  $t$ , (or their equivalent dimensions in other than round tube) are all specified, standard tolerances shall apply to any two of these dimensions, but not to all three. As a result, the purchaser shall only state two nominal dimensions on any given order.

### 3.2 Diameter - Round tube

Mean diameter is defined as the average of two diameter measurements taken at right angles to each other at any position along the length.

The maximum allowable deviation at any point from the specified diameter is the maximum difference measured at any point along the length of the tube, i.e. it is inclusive of any ovality in the cross section.

The tolerances on diameter are specified in Table 1.

As detailed in EN 754-1:2016, Clause 4, if the original order does not make clear the nature of the diameter tolerances required, the supplier shall interpret them as inclusive of any ovality (i.e. maximum allowable deviation at any point from the specified diameter in Table 1). However, the diameter tolerances may be expressed as both mean and inclusive of ovality if this is specifically requested by the purchaser.

**Table 1 — Tolerances on diameter for round tube**

Dimensions in millimetres

Diameter ( <i>OD</i> or <i>ID</i> )		Tolerance on diameter			
		Maximum allowable deviation of mean diameter from specified diameter <sup>e</sup>	Maximum allowable deviation of diameter at any point from specified diameter <sup>a</sup>		
Over	Up to and including		Non-annealed and non heat treated tube <sup>b</sup>	Heat treated tube <sup>c</sup>	Tempers O, H111 and Tx510
≥ 3	8	±0,04 <sup>d</sup>	±0,08 <sup>d</sup>	±0,12 <sup>d</sup>	±0,25 <sup>d</sup>
8	18	±0,05	±0,09	±0,15	±0,30
18	30	±0,06	±0,10	±0,20	±0,40
30	50	±0,07	±0,12	±0,25	±0,50
50	80	±0,09	±0,15	±0,35	±0,70
80	120	±0,14	±0,20	±0,60	±1,2
120	200	±0,25	±0,40	±1,2	±2,4
200	350	±0,38	±0,60	±1,7	±3,4

<sup>a</sup> Not applicable to tubes having a wall thickness less than 2,5 % of the specified outside diameter. The tolerance for tubes with wall thickness less than 2,5 % of the specified outside diameter shall be determined by multiplying the applicable tolerance as follows:

- wall thickness over 2,0 % up to and including 2,5 % of outside diameter: 1,5 × tolerance;
- wall thickness over 1,5 % up to and including 2,0 % of outside diameter: 2,0 × tolerance;
- wall thickness over 1,0 % up to and including 1,5 % of outside diameter: 3,0 × tolerance;
- wall thickness over 0,5 % up to and including 1,0 % of outside diameter: 4,0 × tolerance.

<sup>b</sup> Applies to all alloys in H1x, H2x, H3x tempers, and to alloy EN AW-6063 in the T832 temper.

<sup>c</sup> Applies to all alloys in T3, T4, T6, T66, T73, T8, T9 and Tx511 tempers.

<sup>d</sup> This tolerance applies for outside diameter only, i.e. tube in this size range can only be specified as “Outside Diameter x Wall Thickness”.

<sup>e</sup> Shall not apply to Tx510 or Tx511 tempers.

### 3.3 Width, depth or width across flats - squares, rectangles, hexagons, octagons

The tolerances on width, depth or width across flats are specified in Table 2.

**Table 2 — Tolerances on width, depth or width across flats**

Dimensions in millimetres

Width, depth or width across flats		Maximum allowable deviation of width, depth or width across flats at any point from the specified value <sup>a</sup>		
Over	Up to and including	Non-annealed and non heat treated tube <sup>b</sup>	Heat treated tube <sup>c</sup>	Annealed tube <sup>d</sup>
≥ 8	18	±0,20	±0,30	±0,60
18	30	±0,25	±0,40	±0,80
30	50	±0,35	±0,50	±1,0
50	80	±0,50	±0,70	±1,4
80	120	±0,70	±1,0	±2,0
120	200	±1,0	±1,5	±3,0

<sup>a</sup> Not applicable to tubes having a wall thickness less than 2,5 % of the specified outside width, depth or width across flats. The tolerance for tubes with wall thickness less than 2,5 % of the specified width, depth or width across flats shall be determined by multiplying the applicable tolerance as follows:

- wall thickness over 2,0 % up to and including 2,5 % of outside parameter: 1,5 × tolerance;
- wall thickness over 1,5 % up to and including 2,0 % of outside parameter: 2,0 × tolerance;
- wall thickness over 1,0 % up to and including 1,5 % of outside parameter: 3,0 × tolerance;
- wall thickness over 0,5 % up to and including 1,0 % of outside parameter: 4,0 × tolerance.

<sup>b</sup> Applies to all alloys in F, H1x, H2x, H3x tempers.

<sup>c</sup> Applies to all alloys in T3, T4, T6, T66, T73, T8, T9 and Tx511 tempers.

<sup>d</sup> Applies to all alloys in O, H111 and Tx510 tempers.

### 3.4 Wall thickness variation (eccentricity)

The tolerances on wall thickness variation (eccentricity) for round tubes are specified in Table 3. For other than round tubes the wall thickness variation tolerances shall be agreed between supplier and purchaser.

**Table 3 — Tolerances on wall thickness variation (eccentricity) for round tubes**

Nominal wall thickness <i>t</i> mm		Tolerance on wall thickness variation (eccentricity) %		
Over	Up to and including	For <i>OD</i> < 150	For <i>OD</i> ≥ 150 and < 300	For <i>OD</i> ≥ 300
0,5	3	±7	±9	±11
3	5	±6	±8	±10
5	-	±5	±7	±9

Round tube dimensions can be expressed in three different ways, i.e. outside diameter (*OD*) × wall thickness (*t*), inside diameter (*ID*) × *t* (where *t* is the nominal wall thickness) and *OD* × *ID*. Depending of the way of ordering the tube the values in Table 3 should be understood as follows (see Annex A for further explanation):

- for tubes specified as *OD* × *t* or *ID* × *t* the values are allowable variation at any point;
- for tubes specified as *OD* × *ID* the above values are allowable variation from the calculated mean wall thickness.

### 3.5 Length

If fixed lengths are to be supplied, this shall be stated in the order document. The tolerances on fixed length are specified in Table 4.

**Table 4 — Tolerances on fixed length**

Dimensions in millimetres

Outside diameter or diameter of the circumscribing circle		Tolerances on fixed length				
Over	Up to and including	$L \leq 2\,000$	$2\,000 < L \leq 5\,000$	$5\,000 < L \leq 10\,000$	$10\,000 < L \leq 15\,000$	$15\,000 < L \leq 20\,000$
	100	+5 0	+7 0	+10 0	+16 0	+22 0
100	200	+7 0	+9 0	+12 0	+18 0	+24 0
200	350	+8 0	+11 0	+14 0	+20 0	+28 0

If no fixed length is specified in the order document, porthole tubes may be delivered in random lengths. The length range and the tolerances on the random length shall be subject to agreement between supplier and purchaser.

### 3.6 Squareness of cut ends

The squareness of cut ends shall be within half of the fixed-length tolerance range specified in Table 4 for both fixed and random lengths, (e.g. for a fixed-length tolerance of  $^{+10}_0$  mm the squareness of cut ends shall be within 5 mm).

## 4 Tolerances on form


### 4.1 General

Tolerances on form for O and Tx510 tempers shall be subject to agreement between supplier and purchaser.

### 4.2 Straightness

Deviations from straightness,  $h_s$  and  $h_t$ , shall be measured as shown in Figure 3 with the tube placed on a horizontal base plate so that its mass decreases the deviation.

The straightness tolerances are specified in Table 5. (The straightness tolerance  $h_t$  applies to the whole length, e.g. for a length of 6 m the maximum deviation from straightness  $h_t$  is the value given in the table multiplied by 6 m.)

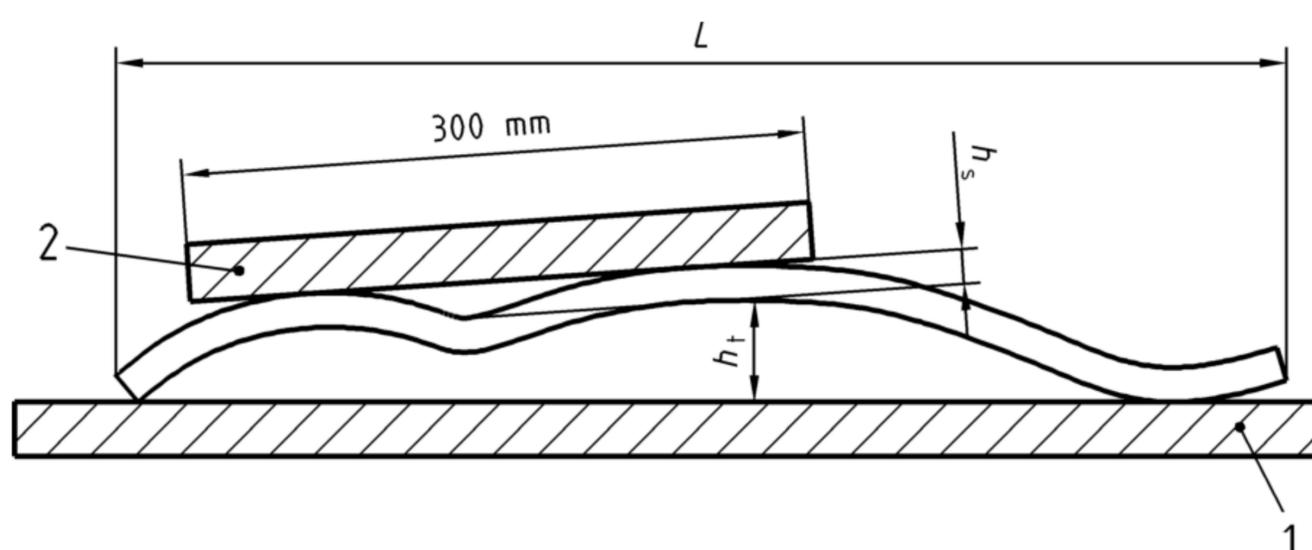

#### Key

- 1 base plate
- 2 straight edge

Figure 3 — Measurement of the deviation from straightness

**Table 5 — Straightness tolerances**


Dimensions in millimetres

Outside diameter or diameter of circumscribing circle		Maximum deviation from straightness per metre length $h_t/length$ mm/m	Maximum localized kink in any 300 mm portion $h_s$
Over	Up to and including		
≥ 8	100	1,0	0,5
100	150	1,5	0,8
150	250	2,0	1,0
250	350	3,5	1,5

Straightness tolerance for tubes having a wall thickness less than 1,5 % the specified outside diameter shall be subject to agreement between supplier and purchaser.

**4.3 Convexity-Concavity**

The convexity-concavity shall be measured as shown in Figure 4. The convexity-concavity tolerances are specified in Table 6.

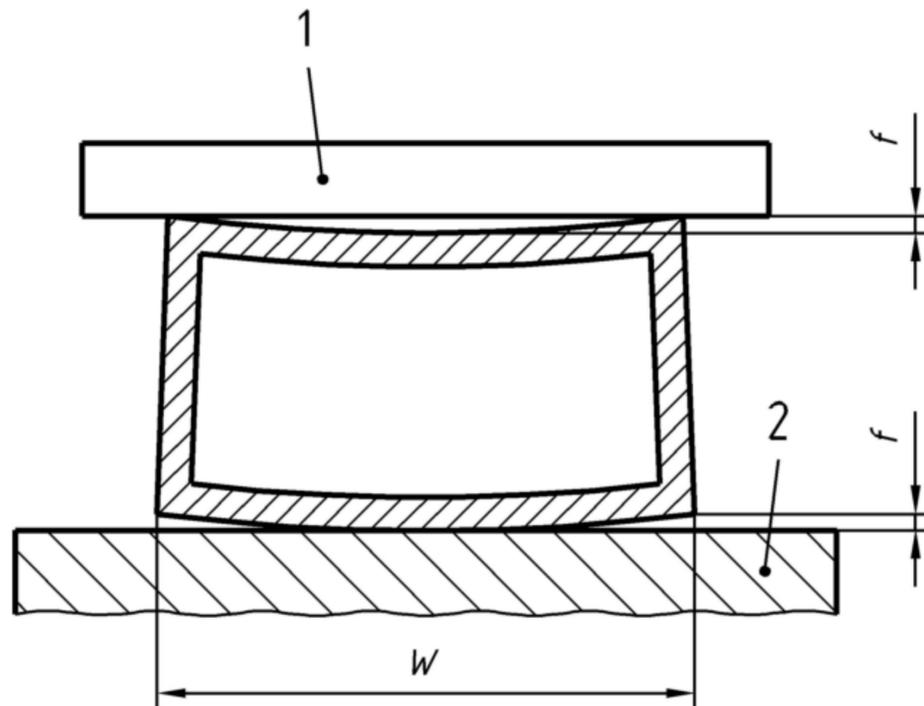

- Key**  
 1 straight edge  
 2 base plate

**Figure 4 — Measurement of convexity - concavity**

**Table 6 — Convexity - concavity tolerances**


Dimensions in millimetres

Width $W$		Maximum allowable deviation $f$	
Over	Up to and including	Wall thickness $\leq 5$	Wall thickness $> 5$
-	30	0,30	0,20
30	60	0,40	0,30
60	100	0,60	0,40
100	150	0,90	0,60
150	200	1,2	0,80

**4.4 Twist**

Twist  $T$  shall be measured as shown in Figure 5 by placing the tube on a flat base plate, the tube resting under its own mass and measuring the maximum distance at any point along the length between the bottom surface of the tube and the base plate surface.

Twist tolerances are specified in Table 7 as a function of the width  $W$  and the length  $L$  of the tube.

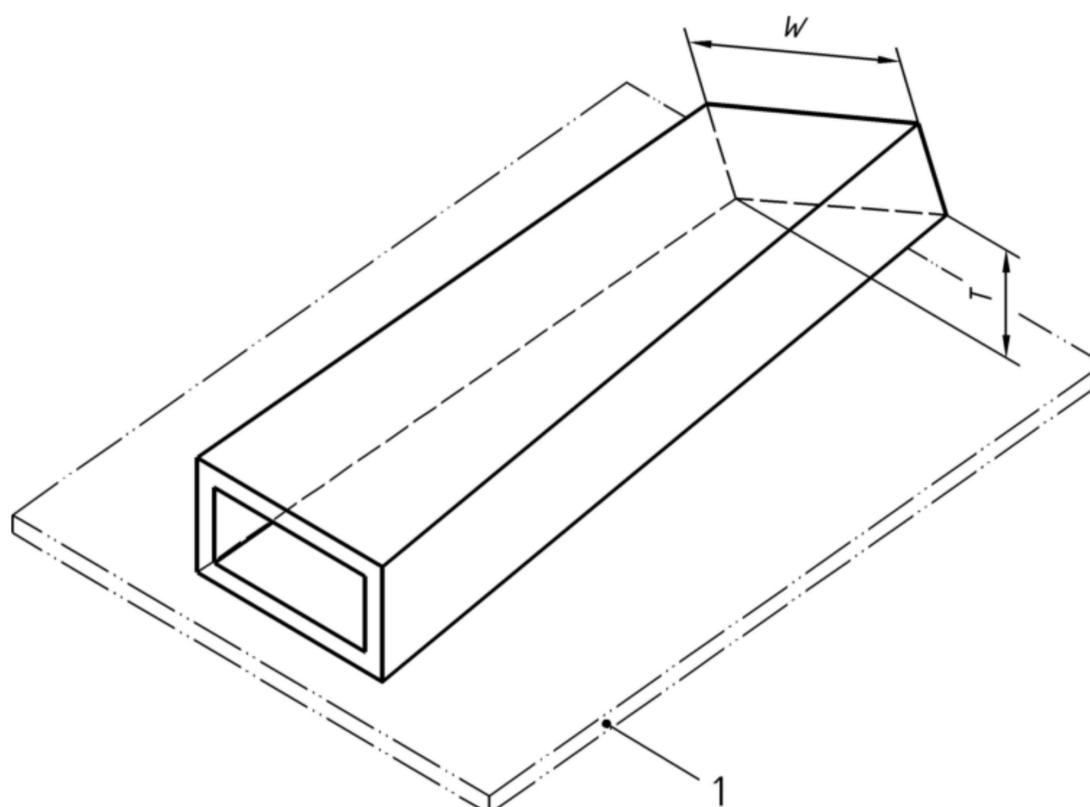**Key**

1 base plate

**Figure 5 — Measurement of twist**

**Table 7 — Twist tolerances**

Dimensions in millimetres


Width $W$		Twist tolerance $T$		
		Per 1 000 mm of length <sup>a</sup>	On total tube length $L$	
Over	Up to and including			Up to and including 6 000 mm
-	30	1,2	2,5	3,0
30	50	1,5	3,0	4,0
50	100	2,0	3,5	5,0
100	200	2,5	5,0	7,0

<sup>a</sup> Twist tolerances for lengths less than 1 000 mm shall be subject to agreement between supplier and purchaser.

**4.5 Angularity**

The deviation from square of square and rectangular tubes shall be measured as shown in Figure 6. The maximum allowable deviation from square is specified in Table 8 as a function of tube depth  $B$ . In the case of rectangular tubes, the tolerance on squareness shall apply to the shorter side of the tube.

The maximum allowable deviation in an angle other than a right angle (hexagonal tubes, octagonal tubes) shall be included within the width across flats tolerances, see Table 2.

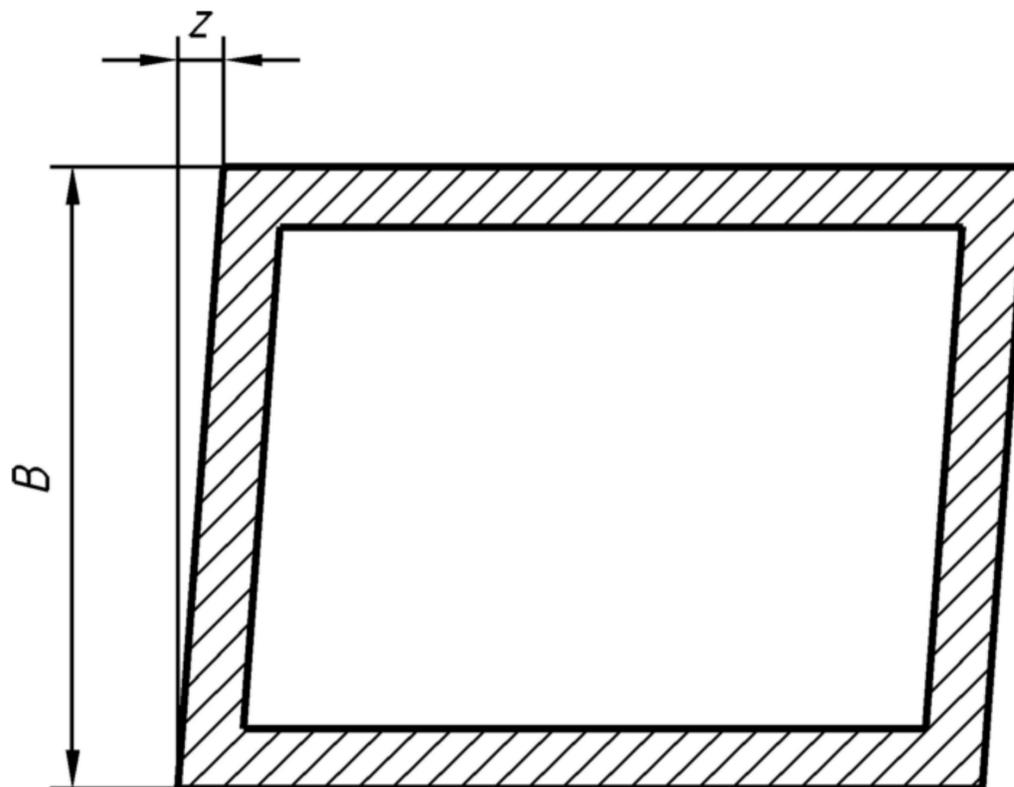

**Figure 6 — Measurement of deviation from square**

**Table 8 — Squareness tolerances for square and rectangular tube**

Dimensions in millimetres

Depth <i>B</i>		Maximum allowable deviation <i>Z</i> From right angle
Over	Up to and including	
-	30	0,4
30	50	0,7
50	80	1,0
80	120	1,4
120	200	2,0

**4.6 Corner and fillet radii**

Sharp corners and fillet radii may be slightly rounded unless otherwise indicated on the drawing. If corner and fillet radii are to be specified, these shall be subject to agreement between supplier and purchaser together with relevant tolerances.

**4.7 Depth of dents for round tubes**

The tolerances for depth of dents for round tubes are specified in Table 9. The tolerances for other than round tube shall be subject to agreement between supplier and purchaser.

**Table 9 — Depth of dents tolerances for round tube**

Dimensions in millimetres

Outside or Inside Diameter		Tolerance on depth of dent <sup>a</sup>		
Over	Up to and including	Non-annealed and non heat treated tube <sup>b</sup>	Heat treated tube <sup>c</sup>	Annealed tube <sup>d</sup>
3	8	0,08	0,12	0,25
8	18	0,09	0,15	0,30
18	30	0,10	0,20	0,40
30	50	0,12	0,25	0,50
50	80	0,15	0,35	0,70
80	120	0,20	0,60	1,20
120	200	0,40	1,20	2,40
200	350	0,60	1,70	3,40

<sup>a</sup> Depth of dents shall not exceed the tolerances specified in Table 9 at any point from the specified diameter, with the following exception: for tube having a wall thickness less than 2,5 % of the outside diameter, the following multipliers to the above tolerances shall apply:  
— wall thickness over 1,5 % up to and including 2,5 % of outside diameter: 1,25 × tolerance;  
— wall thickness over 0,5 % up to and including 1,5 % of outside diameter: 1,5 × tolerance.

<sup>b</sup> Applies to all alloys in F, H1x, H2x, H3x tempers and to alloy EN AW-6063 in the T832 temper.

<sup>c</sup> Applies to all alloys in T3, T4, T6, T66, T73, T8, T9 and Tx511 tempers.

<sup>d</sup> Applies to all alloys in O, H111 and Tx510 tempers.

## Annex A (informative)

### Wall thickness variation (eccentricity)

#### A.1 General


Wall thickness variation tolerances for round tube can be the source of a lot of confusion. In particular as to whether quoted values are based on the nominal or mean wall thickness. This present section is included in the standard to provide some guidelines as to when each of these possibilities is more appropriate.

#### A.2 Specifying round tube sizes and tolerances

##### A.2.1 General

It is evident that round tube dimensions can be expressed in three different ways, i.e. outside diameter ( $OD$ )  $\times$  wall thickness ( $t$ ), inside diameter ( $ID$ )  $\times$   $t$  (where  $t$  is the nominal wall thickness) and  $OD \times ID$ . Since all three dimensions interact in any given size tube, it is only possible to apply tolerances to any two of the parameters depending on which are the most important for the application of the tube in question. The choice of the dimensional parameters has a very significant effect on how the wall thickness variation is expressed.

The method of measuring wall thickness ( $t$ ) is the same whether the given tube is specified as  $OD \times t$ ,  $ID \times t$  or  $OD \times ID$  and is shown in Figure A.1. The tube wall thickness is measured around the circumference of the tube and the maximum ( $t_{\max}$ ) and minimum ( $t_{\min}$ ) values established.

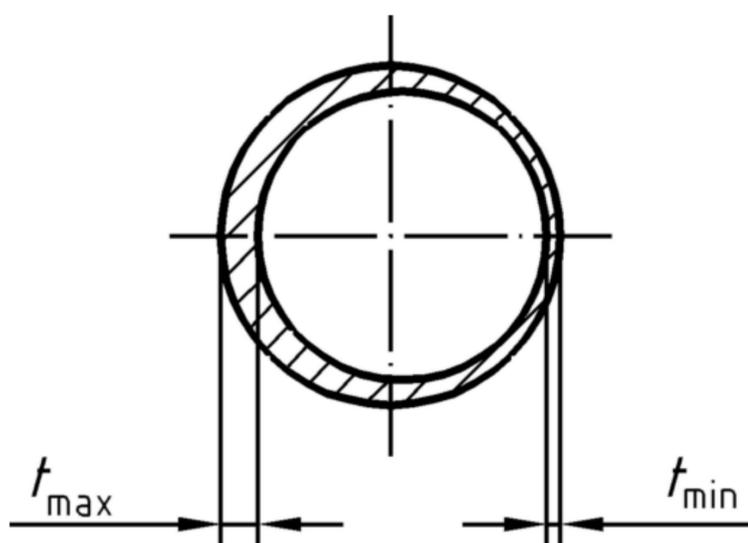

**Figure A.1 — Minimum and maximum values of the tube wall thickness**

##### A.2.2 Wall thickness variation for tubes specified as $OD \times t$ or $ID \times t$

For tube that is specified as either  $OD \times t$  or  $ID \times t$ , the nominal wall thickness  $t$  can be used as the basis for calculating and expressing the wall thickness variation tolerance. The tolerance can be expressed as the difference (in millimetres) between the maximum and minimum values permissible for the tube, i.e. at any point, maximum wall thickness variation, deviation or concentricity:

$$t_{\max} - t_{\min} \text{ in mm} \quad (\text{A.1})$$

Alternatively, the difference can be expressed as a percentage of the nominal wall thickness which is normally divided by two to give a plus and minus tolerance. This percentage is normally expressed on a  $\pm$  basis as follows:

$$\frac{t_{\max} - t_{\min}}{2t} \times 100 \% \quad (\text{A.2})$$

### A.2.3 Wall thickness variation for tubes specified as *OD* $\times$ *ID*

In the case of tubes specified as *OD*  $\times$  *ID*, there is no nominal wall thickness available to allow the same method of wall thickness variation calculation as that described in A.2.2. As a result, it is necessary to use the measured  $t_{\max}$  and  $t_{\min}$  values to give a wall thickness difference which is then used to calculate a percentage of the mean wall thickness.

$$\frac{t_{\max} - t_{\min}}{(t_{\max} + t_{\min})/2} \times 100 \% \quad (\text{A.3})$$

This value may then be divided by two to give a plus/ minus value for the tolerance.

## Bibliography

- [1] EN 515, *Aluminium and aluminium alloys — Wrought products — Temper designations*
- [2] EN 754-7, *Aluminium and aluminium alloys — Cold drawn rod/bar and tube — Part 7: Seamless tubes, tolerances on dimensions and form*
- [3] EN 13958, *Aluminium and aluminium alloys — Cold drawn, round, coiled tube for general applications — Specification*

